

## Multi-technical approach for the characterization of polychrome decorative surfaces at Spanish Mission Churches in Nueva Vizcaya (Chihuahua, Mexico)

Karla Muñoz-Alcocer , Laura Fuster-López , Ma. Luisa Vázquez de Ágredos-Pascual , Francesca Caterina Izzo , Marcello Picollo , Giovanni Bartolozzi , Jose Humberto Vega , Diana Maldonado Escobar , Alejandro Mitrani , Miguel Ángel Maynez , Edgar Casanova-González , Isaac Rangel-Chávez & Jose Luis Ruvalcaba-Sil

To cite this article: Karla Muñoz-Alcocer , Laura Fuster-López , Ma. Luisa Vázquez de Ágredos-Pascual , Francesca Caterina Izzo , Marcello Picollo , Giovanni Bartolozzi , Jose Humberto Vega , Diana Maldonado Escobar , Alejandro Mitrani , Miguel Ángel Maynez , Edgar Casanova-González , Isaac Rangel-Chávez & Jose Luis Ruvalcaba-Sil (2019) Multi-technical approach for the characterization of polychrome decorative surfaces at Spanish Mission Churches in Nueva Vizcaya (Chihuahua, Mexico), STAR: Science & Technology of Archaeological Research, 5:2, 287-304, DOI: [10.1080/20548923.2020.1763054](https://doi.org/10.1080/20548923.2020.1763054)

To link to this article: <https://doi.org/10.1080/20548923.2020.1763054>



© 2020 The Author(s). Published by Informa UK Limited, trading as Taylor & Francis Group



Published online: 20 Jul 2020.



[Submit your article to this journal](#)



Article views: 263












[View related articles](#)



[View Crossmark data](#)

## Multi-technical approach for the characterization of polychrome decorative surfaces at Spanish Mission Churches in Nueva Vizcaya (Chihuahua, Mexico)

Karla Muñoz-Alcocer <sup>a,b,c</sup>, Laura Fuster-López <sup>d</sup>, Ma. Luisa Vázquez de Ágredos-Pascual <sup>e</sup>, Francesca Caterina Izzo <sup>f</sup>, Marcello Picollo <sup>g</sup>, Giovanni Bartolozzi<sup>g</sup>, Jose Humberto Vega <sup>h</sup>, Diana Maldonado Escobar<sup>c</sup>, Alejandro Mitrani <sup>i</sup>, Miguel Ángel Maynez<sup>i</sup>, Edgar Casanova-González <sup>j</sup>, Isaac Rangel-Chávez<sup>i</sup> and Jose Luis Ruvalcaba-Sil <sup>i</sup>


<sup>a</sup>Misiones Coloniales de Chihuahua A.C., Chihuahua, Mexico; <sup>b</sup>Laboratorio de Patrimonio Histórico, Chihuahua, Mexico; <sup>c</sup>Tecnológico de Monterrey Campus Chihuahua, Chihuahua, Mexico; <sup>d</sup>Instituto Universitario de Restauración del Patrimonio, Universitat Politècnica de València, València, Spain; <sup>e</sup>Dpto. Historia del Arte, Universidad de Valencia, València, Spain; <sup>f</sup>Scienze e tecnologie per la conservazione dei beni culturali, Ca' Foscari University of Venice, Venezia, Italy; <sup>g</sup>Istituto di Fisica Applicata "Nello Carrara" (IFAC-CNR), Sesto Fiorentino, Italy; <sup>h</sup>Fac. de Zootecnia and Ecology, Universidad Autónoma de Chihuahua, Chihuahua, Mexico; <sup>i</sup>Instituto de Física, Universidad Nacional Autónoma de México, Mexico City, Mexico; <sup>j</sup>CONACYT-Instituto de Física, Universidad Nacional Autónoma de México, Mexico City, Mexico

### ABSTRACT

An interdisciplinary and multi-institutional group of science and art conservation specialists has provided new insight into the painting materials used in the polychrome walls and wooden ceilings in four seventeenth century Spanish colonial churches of Nueva Vizcaya (Chihuahua, Mexico). A multi-analytical study of the decorative surfaces was performed in situ using spectroscopic approaches (XRF, FORS), False Colour Infrared Reflectography – IRFC, as well as micro sampling for ATR-FTIR, LM and GC/MS laboratory analyses. A survey of natural resources were also studied by ATR-FTIR and LM to elucidate the natural occurrence of a select number of materials found in the surrounding areas of the churches. The present paper presents a multi-analytical study and characterization of green, red-orange and black colour pigments and binders selected from the decorative surfaces. The aim of this study is to highlight relationships between local materials and those from the original polychrome ceilings, in order to understand the material and technological influences that converged in the Spanish colonial architecture of northern Mexico.

### KEYWORDS

Spanish colonial missions; Chihuahua; tascate; multi-analytical study; Santa Maria de Cuevas; Polychrome wooden ceilings

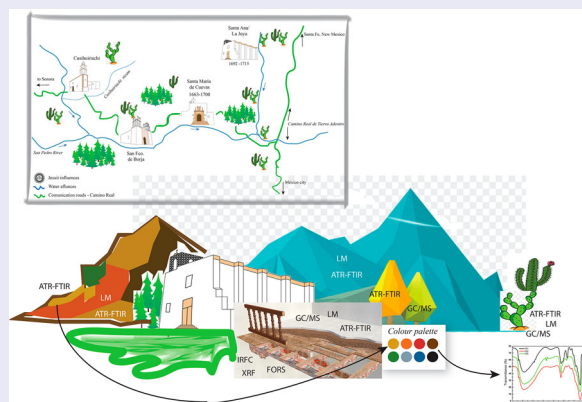

## 1. Introduction

In the last five years, a multi-technical research project on the analysis of decorative surfaces of four seventeenth century Spanish Jesuit colonial churches of Nueva Vizcaya (Chihuahua, Mexico) (Marquez 1995, 2008) has been carried out by an interdisciplinary and multi-institutional group of specialists. In addition, a natural resources survey was implemented (Muñoz Alcocer 2018) in order to determine the influences and sources of the original artists' materials (Muñoz-

Alcocer et al. 2016). Thus, the study was focused on identifying those materials that were available locally, due to their natural occurrence in the surrounding areas of the churches, and differentiating them from those likely imported through the royal trade that connected Mexico City with the Northern Spanish frontier.

This paper presents the analysis of the materials used to produce the polychrome surfaces of four Spanish Colonial Churches located at Santa Maria de Cuevas (SMC), Cusihuirachi (CUSI), San Francisco de

**CONTACT** Karla Muñoz-Alcocer  [karla@misionescoloniales.org](mailto:karla@misionescoloniales.org)


This article has been republished with minor changes. These changes do not impact the academic content of the article.

© 2020 The Author(s). Published by Informa UK Limited, trading as Taylor & Francis Group

This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0/>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Borja (SJB), and Santa Ana (ANA). In addition, the paper describes the analysis of the natural materials collected in the localities of the four churches. This analysis was carried out in order to determine the role, if any, local materials played in producing paints that could have been used in the decoration of the churches' interiors (Figure 1). For this purpose, the characterization of dyes and pigments of the decorative surfaces was carried out *in situ* by X-ray fluorescence and fibre optic reflectance spectroscopy together with laboratory techniques that required micro samples, such as infrared spectroscopy, light microscopy, and Gas Chromatography integrated Mass spectroscopy. False colour infrared imaging technique was also used to document and study the investigated surfaces. The collected local natural materials (plants, extracts, rocks, clay and river water) around the four sites were used to reproduce representative mock-ups following ancient painting techniques. The first results on these mock-ups showed the significant influence of water from the nearby Rio San Pedro. A well correlated match was found between the spectra from samples taken from the decorative surfaces and those from mock-ups that were prepared with local water (Muñoz-Alcocer, et al. 2017b).

The previous analytical results have also revealed the use of iron oxide based pigments, which were well known by the local Indian community. Indigo, cochineal, malachite and red lead (minium) -which had not been previously documented in Chihuahua's Tarahumara Indians' palette (González 1972; Pennington 1963) – were also found (Muñoz Alcocer 2018). The presence of *Indigofera Suffruticosa* had already been registered by local botanists at the deeper levels of the Sierra Tarahumara Canyons, located an eight-hour distance from the studied area (Lebgue Keleng 2001). A cactus (*Opuntia*) with a manifest of cochineal was found at one of the church towns as well. Considering that indigo and carmine dyes had a great economic and symbolic value in pre-Hispanic times, and that therefore both colours were exchanged through the trade routs of ancient Mesoamerica as described in historical writings (e.g. Matricula de Tributos, ca.1522-30; Berdan & de Durand 1980; Sahagún 1577; Sarabia Viejo 2004), it could be possible that such dyes and pigments were produced locally and traded. The characterization of indigo (Gettens 1962; Gettens et al. 1946; Vázquez de Ágredos Pascual et al. 2014; Doménech et al. 2014) and cochineal (Dahlgren de Jordan 1954) in these decorative ceilings had been documented previously (Muñoz-

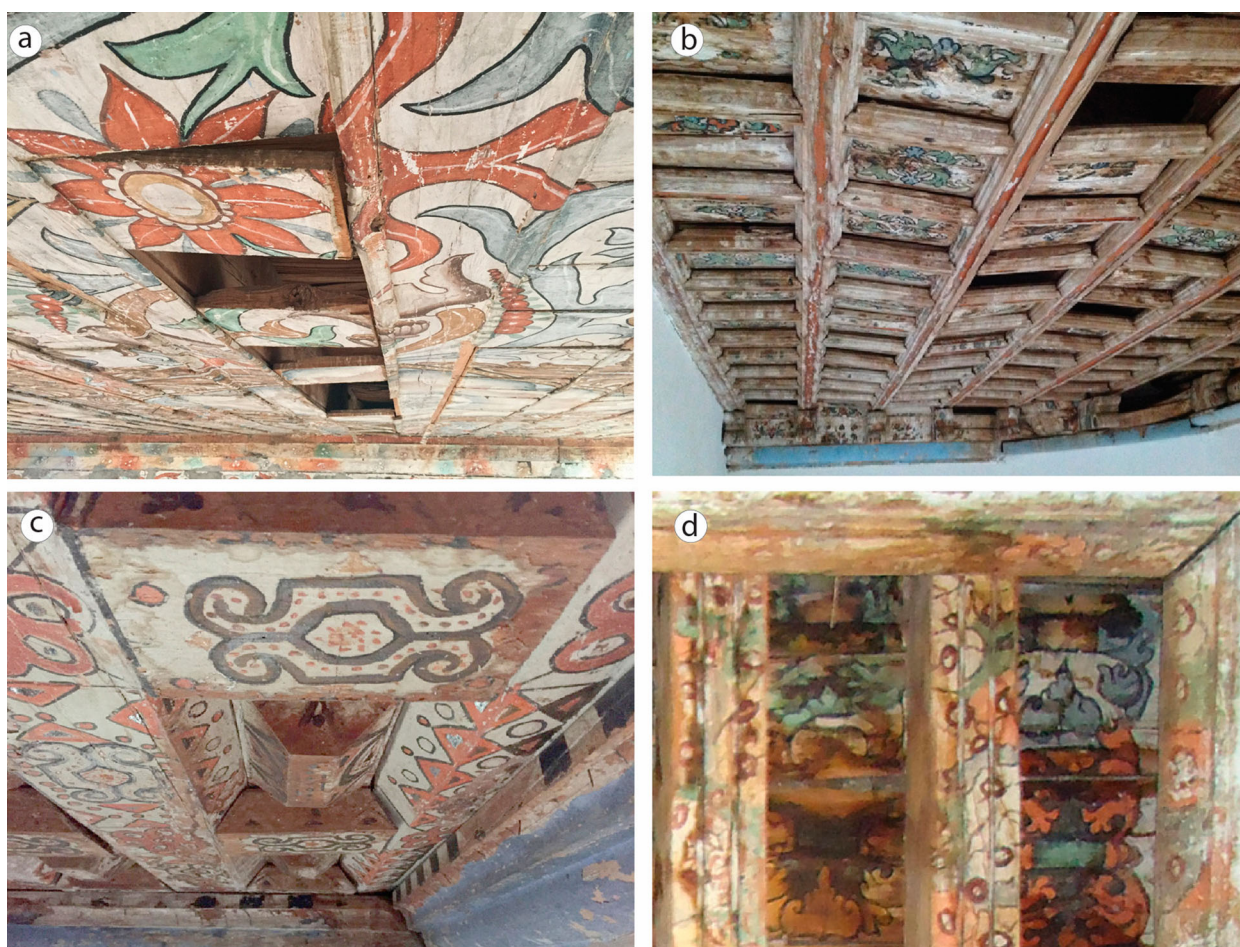

**Figure 1.** Detail of the polychrome wooden ceilings from Santa Maria de Cuevas (a); Cusihiuriachi (b); San Francisco de Borja (c) and Santa Ana de la Joya (d). K. Muñoz Alcocer, 2015.



**Table 1.** Invasive and non-invasive techniques used to characterize *in situ* spot tests and microsamples of the four sites studied.

Analytical techniques	Santa Maria de Cuevas																Cusihuiachi										San Francisco de borja					Santa Ana de la Joya																				
	Nave & Presbitero								Narthex								Chapel										Baptistry					Presbitero & Narthex																				
	W		G		Y		R		B		G		W		G		Y		R		B		G		W		G		Y		R		B		G		W		G		Y		R		B		G					
Non-invasive	IR-FC	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓			
	XRF	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓		
	FORS	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	
Invasive	LM	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	
	ATR-FTIR	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓	✓
	RAMAN					✓	✓																																													
	GC-MS	✓		✓		✓												✓																																		

Alcocer, et al. 2017b). Results indicated that indigo was either mixed with gypsum (as *ad hoc* Maya blue pigment) or applied directly to the gypsum ground surface following the European technique (Cennini 1954; Doerner 1984). As for cochineal, two sources were used: domesticated cochineal from Lanzarote (Spain), and sylvan cochineal collected at Santa Maria de Cuevas town. In FTIR spectra, very little correlation difference was detected between the domesticated (96%) and the sylvan cochineal (97%) mixed with alumina (3:1) FTIR spectra. Nevertheless, alumina was identified as mordant (Muñoz Alcocer 2018).

The current paper establishes the correlations found using ATR-FTIR between the collected natural resources and the identification made by the multi-analytic studies of other colours such as green (malachite and mixture of malachite, indigo and green & yellow earth), red-orange (minium) and black (carbon and iron oxide). Local resin-gums, which could have been used as binders in the polychrome wooden ceilings of the four case studies were also analysed.

## 2. Materials and methods

The analysis of micro samples together with *in situ* measurements in SMC, CUSI, SFB and ANA was carried out. Samples from collected regional materials such as malachite, lead, yellow, black and red earths were analysed and used for mock-up preparation. The indigo used was from a family of dyers in Oaxaca, who continue to make the dye using traditional methods. The dyes as well as the raw materials used in their manufacture, were also analysed for comparison purposes before they were used in the mock-ups. The sample preparation and analytical methods are presented in two sub-sections: micro-invasive and non-invasive analysis techniques in microsamples from the case studies, and regional materials and mock-ups.

### 2.1. Case studies

*Non-invasive in situ study for actual case studies and analysis of samples.* In 2015 samples were taken from


the four case studies. In 2016, IRFC images were registered and spectroscopic measurements by XRF, FORS were carried out at the same areas where samples had been taken (Aceto et al. 2012a; Aceto et al. 2012b; Appolonia et al. 2009; Bacci et al. 2009; Mounier et al. 2014; Leona and Winter 2001). Table 1. Summarizes the points and samples considered in the multi-analytical study in the four sites SMC, CUSI, SFB, ANA.

### 2.2. Mock-ups and local materials

The local materials collected were observed under the microscope and analysed with ATR-FTIR. Representative mock-ups were made for the characterization of ground layers, colour pigments, and dyes. A ground made of calcium sulphate ( $\text{CaSO}_4$ ) and calcium sulphate hemihydrate ( $\text{CaSO}_4 \cdot \frac{1}{2} \text{H}_2\text{O}$ ) was applied to two pine wood panels. Two different painted areas were created for each panel: in one area the paint layer was applied with no binder (in order to obtain a clear interpretation of the colour palette). In the other hand, the resin-gum, tascate (*Juniperus deppean*), was used as a binding medium in order to determine its use as a binder at the selected polychrome wooden ceilings.

Malachite, indigo, green and yellow earth were used in the production of pigments to explore the use of either green earth, malachite or a mixture of malachite, indigo and yellow or green earth in the green areas studied at Santa Maria de Cuevas, Cusihuiachi and Santa Ana (Figure 2). The identification of the red-orange (minium), black, and ground layer was made by ATR-FTIR spectra comparisons with lead (Pb) from local mines, local earths (brown, red and black), as well as burnt wood gypsum, lime, and tascate resin that were collected around the selected case studies.

Local water sources were used in the production of pigments and mock-ups as their geographical proximity to the case study was likely noted and utilized by the original artists. Outflow water from the mines located near the mining town of Cusihuiachi merge with water from the confluence of the San Pedro River and a smaller local stream, making them a readily available source both in the past and now. The

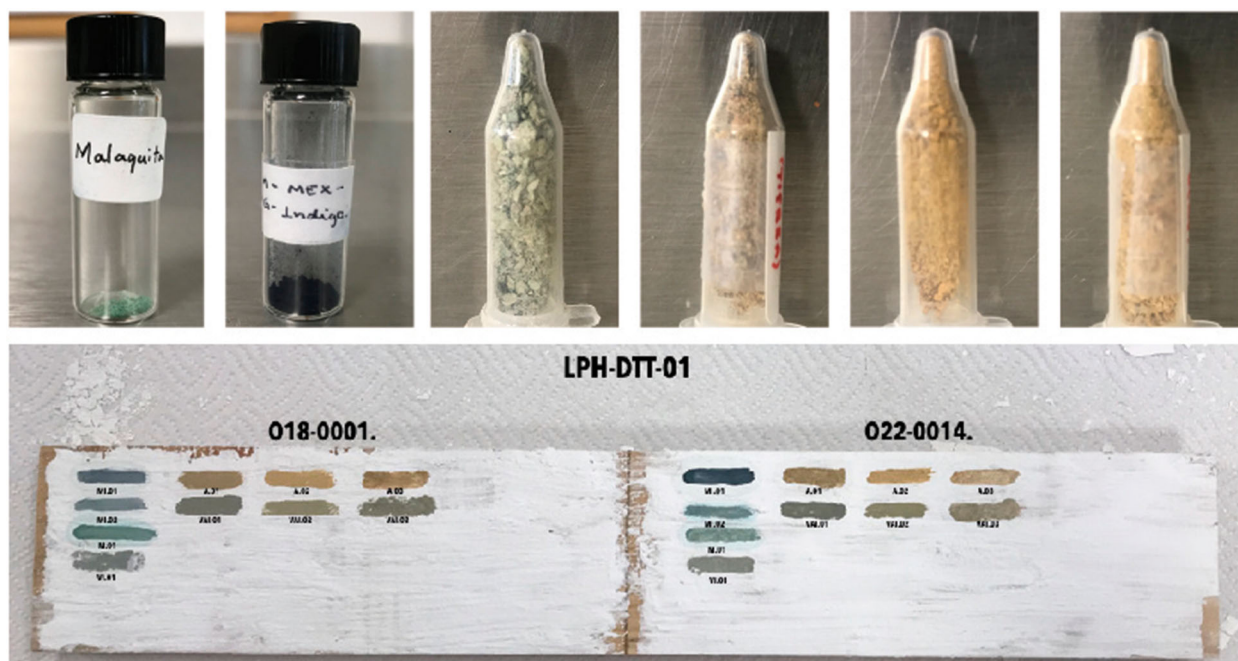

**Figure 2.** Characterization of the green colours from Santa María de Cuevas and Cusihuirachi ceilings. View of the materials used and the mock-ups prepared with their identification number.

mock-ups were divided into two sections as a function of the water used (Table 2).

### 2.3. Analytical methods

#### 2.3.1. Non-invasive

*False Colour Infrared (IRFC).* Photographs under Infrared (IR) and visible radiation (VIS) were registered in order to create a False Colour image (FCIR). This is done by overlapping both pictures, and a new colour scale is produced. In this case, a Sony Handycam camera HDR-PJ760 with an IR Filter 760 nm was used. In addition, Lowe Totta lamps of 750W with halogen bulbs of 3200K were used for

illumination. The FCIR is generated by merging the RG channels with the infrared image. FCIR is obtained when the B channel is given to the imaged G channel, the G channel to the imaged R channel, and the R channel to the acquired IR image. The final result of the new RGB image is a False Colour image (Warda et al. 2011). FCIR photographs were observed using an Apple MacBook OS X El Capitan with a screen calibrated in RGB Adobe (1998). Grey dot gain 20% and spot gain 20%.

*X-Ray fluorescence (XRF).* Spectra were acquired with a Tracer-III SD (Bruker) handheld spectrometer. Acquisition conditions were 40 kV, 11  $\mu$ A for 30 s per region. All spectra were processed with the software

**Table 2.** Materials used in the elaboration of the representative mock-ups for the characterization of ground layers, colour pigments, and dyes.

Water source	Wood	Ground	Code	Malachite (g)	Indigo (g)	Green earth (g)	Yellow earth (g)	water (Drops)	Vinegar (drops)
San Pedro river water PH-DTT-01 022-0014	Pine wood	CaSO <sub>4</sub> + H <sub>2</sub> O SMC + Tascate resin-gum	MI.01	0.02	0.01	–	–	4	2
			MI.02	0.01	0.001	–	–	2	1
			M	0.035	–	–	3	2	
			VI	–	0.005	0.308	–	8	4
			AA	–	–	–	0.305	5	3
			AB	–	–	–	0.305	5	3
			AC	–	–	–	0.306	5	3
			VAIA	–	0.01	0.2	0.2	6	4
			VAIB	–	0.01	0.2	0.2	6	4
			VAIC	–	0.01	0.2	0.2	6	4
			Cusihuirachi steam water LPH-DTT-01 018-0001		CaSO <sub>4</sub> + H <sub>2</sub> O CUSI + Tascate resin-gum	MI.01	0.02	0.01	–
MI.02	0.01	0.001				–	–	2	1
M	0.035	–				–	3	2	
VI	–	0.005				0.308	–	8	4
AA	–	–				–	0.305	5	3
AB	–	–				–	0.305	5	3
AC	–	–				–	0.306	5	3
VAIA	–	0.01				0.2	0.2	6	4
VAIB	–	0.01				0.2	0.2	6	4
VAIC	–	0.01				0.2	0.2	6	4

Spectra Artax v.7.4.6.1 (Bruker) in order to measure the X-ray intensities.

*Fibre Optics Reflectance Spectroscopy (FORS)*. *In situ* FORS analysis was performed using a portable Field-Spect-4 spectroanalyser by ASD Inc., equipped with optical fibre bundles. Spectra were acquired in the 300–2500 nm range with 10 nm spectral resolution. The probe-head covers a 1 cm<sup>2</sup> area and is equipped with a halogen lamp. All spectra were recorded in reflectance and then saved in both reflectance and apparent absorbance (Log [1/R]) modes, with a 0.2 seg. integration time. A certified reflectance standard provided by ASD Inc (AS-02035-000CSTM-SRM-990-362) was used for calibration. FORS spectra were compared with spectral databases and reference samples for the identification of pigments and other materials.

Additionally, UV-Vis-NIR (350–2200 nm) FORS data were also acquired on a panel piece of the polychrome nave ceiling of Santa Maria de Cuevas at IFAC-CNR, Sesto Fiorentino, Florence, Italy. Two Zeiss spectra analysers (models MCS 601 UV/VIS and MCS 611 NIR 2.2 WR, respectively) were used. The radiation between 320 and 2700 nm, which was provided by a voltage-stabilized 20w halogen lamp (module Model CLH600), was conveyed to the sample by means of a quartz optical fibre bundle that also transported the reflected radiation to the detectors. A 8°/8° probe-head, which can investigate an approximately 2-mm diameter spot was used. A 99% Spectralon® diffuse reflectance standard was used to calibrate the system.

### 2.3.2. Micro- Invasive analytical studies

*Optical light microscopy (LM)*. Samples were observed in detail using a Stereomicroscope Olympus SZX16 with a 1XPF Palapo lens. Photos were taken with a Nikon Camedia C-5050 camera in automatic mode at 300 dpi.

Cross-sections were prepared in an epoxy resin (Epo-Tek 301-1), the two components (resin and sensitizer) were mixed and cured at ambient temperature (23°C) for 24 h. Each sample was encapsulated with the sample code on a label. Samples were studied and photographed with an Olympus BX51 optical microscope equipped with transmitted and reflected light with bright field, dark field and polarized light. In addition, a selected number of samples were also photographed with a DINOLite microscope under visible (VIS) and ultraviolet (UV) light in order to identify where organic components may be located.

**2.3.2.1. Infrared spectroscopy in Attenuated Total Reflectance mode (ATR-FTIR)**. A Bruker Alpha-P ATR-FTIR spectrophotometer equipped with a Platinum ATR sampling module (diamond crystal) was used to collect spectra in the 4000–400 cm<sup>-1</sup> range.

The spectra were examined with Quick Compare OPUS software. ATR-FTIR spectra obtained were compared to the spectral library of traditional and natural resource materials (cochineal, azurite, malachite, lead, natural earths, etc.) created at Laboratorio de Patrimonio Histórico (LPH). The unlimited access to the equipment and software made infrared spectroscopy the predominant analytical technique. The interpretation of results was based on ATR-FTIR spectra and their correspondence with the results from the other analytical studies. The abbreviations used to describe the intensity of absorption bands are the following: (s) strong; (m) medium; (w) weak; (br) broad; (sh) sharp; (d) deformation and (p) present. In some cases, a combination of these abbreviations is used (e.g. "ms" for medium strong).

*Gas chromatography-mass spectrometry (GC-MS)* analyses were carried out to identify the organic binding media present in the paint and ground layers. For this purpose, two different procedures developed by Conservation Science research group at Ca' Foscari University (Venice) were used. For lipidic, waxy and resinous materials, the samples were transesterified using (trifluoromethylphenyl) trimethylammonium hydroxide, an overnight reaction as described in (Fuster Lopez et al. 2016; Izzo 2011; Izzo et al. 2014a; Izzo et al. 2014b). GC-MS analyses were performed using an Agilent 6890N GC instrument with a capillary HP-5 column, 30 m, 0.25 mm, 0.5 µm interfaced with an 5973 Network MS. The temperature programme was set from 80 °C to 300 °C with a ramp of 10°C/min, held at 300°C for 2 min. The MS was run in Full Scan mode (m/z 40–600), 1.9 scans/s. Quantitative GC-MS analysis was performed using nonadecanoic acid as internal standard. For proteinaceous and polysaccharidic materials, amino acids and carbohydrates were analysed as N,O-acetyl methyl esters after hydrolysis with trifluoroacetic acid and derivatisation (Henk Van Keulen of the Cultural Agency of the Netherlands and then implemented by Francesca C. Izzo at Ca' Foscari University of Venice). GC-MS analysis were performed using an Agilent 6890N GC instrument with a capillary Carbowax Column, 30 m, 0.20 mm, 0.5µm interfaced with an 5973 Network MS. The temperature programme was set from 80 to 250°C, with a ramp of 20°C/min until 210, then 2°C/min until 250°C. The MS was run in Full Scan mode (m/z 40–500). Mannitol and Norleucine were used as internal standards.

## 3. Results

### 3.1. Ground layer

Natural occurring deposits of gypsum and calcite are present in the region of study. In San Francisco de Borja, a clay kiln oven traditionally used to burn calcite

was found. In Santa Maria de Cuevas, the deposit of gypsum is a little farther from the mission than that of calcite. Clay ovens to burn calcite, as well as those traditionally used to heat clay vessels and to bake bread, are found associated with the patios of the houses built under Spanish colonial influences.

Gypsum is present in the ground layer of Santa Maria's nave ceiling, at Cusihuirachi, and at San Francisco de Borja. Anhydrite and hemihydrate sulfate (Hunt et al. 1950, 427), are also present in some FTIR spectra. In Santa Maria, some weak bands ( $875, 711 \text{ cm}^{-1}$ ) of calcium carbonate ( $\text{CaCO}_3$ ) were detected as well in some spectra from the ground layer. Calcium carbonate ( $1429\text{s}, 872\text{sh}, 712\text{psh} \text{ cm}^{-1}$ ) was used as the main ground component at the narthex ceiling of Santa Maria. In addition, absorption bands related to anhydrite ( $670\text{msh}, 614\text{p}, 593\text{msh} \text{ cm}^{-1}$ ) and hemihydrate sulphate ( $3600\text{p}, 3440\text{p}, 1151\text{ms}, 1120\text{sh}, 1690\text{p}, 667\text{def}, 466\text{p} \text{ cm}^{-1}$ ) and dihydrate ( $3544\text{m}, 3407\text{m}, 3250\text{br}, 1109, 490\text{p}, 414\text{psh} \text{ cm}^{-1}$ ) were also detected in the narthex ceiling of Santa Maria de Cuevas.

The use of calcium carbonate as the ground layer at the narthex ceiling in Santa Maria could have been for aesthetic impact. In fact, a ground layer whiter than gypsum was needed to contrast the white-grey grisaille used to decorate the painted panels and to create a perspective effect. (Muñoz Alcocer 2018, 263). Another reason could be related to the painting technique and the type of wood that was chosen; however, further studies need to be done in order to attribute the use of calcium carbonate as a ground layer due to these two factors.

In Santa Ana de la Joya, only calcium carbonate was detected. It is uncertain why calcite was chosen by the painter, and could simply be that these materials were


more readily available. However, gypsum was present in Santa Ana and was used in the preparation of some pigments. Clearly, the use of this material for artistic purposes was known, and that its substitution by calcium carbonate at the underlying levels was an intentional choice- as found in a red-orange sample taken from the bearing beam of the choir in Santa Ana. Here, it is most likely that the red and yellow ochre were mixed with gypsum to create the orange colour instead of having gypsum applied for the ground layer. Also traces of gypsum were detected in blue areas (Hunt et al., 1950, 427). In this case, the blue colour was obtained by mixing an unidentified dye with gypsum ( $3408\text{br}, 1622\text{m}, 672\text{sh}, 610\text{sh}, 592\text{sh} \text{ cm}^{-1}$ ) to produce the desired hue. These findings were supported by XRF and FORS data (Figure 3).

ATR-FTIR spectra from samples taken from the mock-ups prepared with calcium sulphate and hemihydrate mixed with tascate resin-gum were compared with those from the ground layer of the case studies. A significant correlation was obtained with Santa Maria de Cuevas (94%) and Cusihuirachi (90%), but lower with San Francisco de Borja (65%). Also of significance is that the ground layer prepared with hemihydrate sulphate and tascate resin-gum, produced grey lines similar to those observed in the ground layer of Santa Maria de Cuevas, but not in the ground layer of the other case studies (CUSI,SFB,ANA) (Figure 4).

### 3.2. Paint layers: pigments and dyes

#### 3.2.1. Green

The visual comparison between the VIS image and FCIR allows the identification of some hue changes

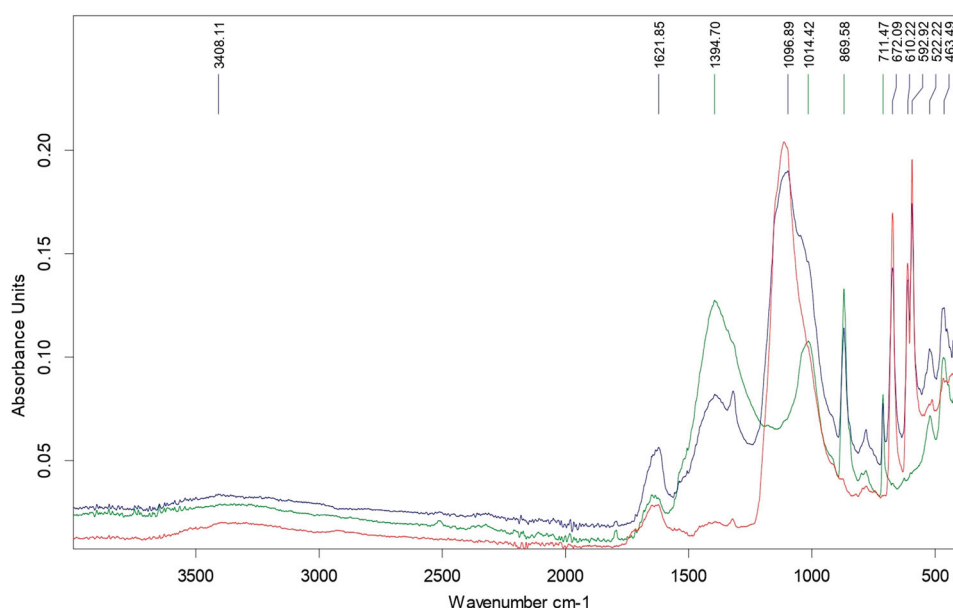

**Figure 3.** ATR-FTIR spectra from the blue (B.T.02) (blue line), red-orange (VM.01) (red line), and ground layer (B.T.04) (green line) from Santa Ana de la Joya narthex and baptistery ceiling. Differences can be observed with the calcium carbonate ground layer absorption bands (peaks on blue) and those from the blue and orange samples spectra, where calcium sulfate absorption bands are present. (K. Muñoz Alcocer, 2019).





**Figure 4.** Santa Maria de Cuevas nave ceiling panel (a) compared with the mock-ups prepared. The ground layer prepared with hemihydrate sulphate and tascate resin-gum presents the same grey strips as the ceiling panel (c) which are not present in the gypsum ground layer prepared without tascate resin-gum (b). K. Muñoz-Alcocer, 2018.

in the green colour. In comparison to other colours, green is the colour that changes the most. This variability is possibly related to the pure condition and aging of

the paint layer, and also to the colour preparation. Different green hues can be seen at Santa Maria de Cuevas (green-yellow and bluish green), Cusiuhiriachi (dark green and bluish-yellow green), and Santa Ana (Dark & light green). These chromatic hues can be better distinguished in the FCIR (Figure 5). For example, Santa Marias' green-yellow leaf motifs appear blue and greenish blue in FCIR. The leaves that in VIS light have a bluish green hue, are reproduced in FCIR as a bright blue with some tendency to red-purple. FCIR studies gave some hints on the possible composition of the green areas, which could have been painted with malachite ( $\text{Cu}_2\text{CO}_3(\text{OH})_2$ ). This pigment, indeed, appears with a bluish hue (Bevilaqua, Borgioli, and Gracia 2010, 241; Moon, Schilling, and Thirkettle 1992, 49), whereas, earth green pigments are rendered with a black or dark blue tint (Bevilaqua, Borgioli, and Gracia 2010, 259; Moon, Schilling, and Thirkettle 1992, 49).

The physical condition of the painted surfaces can affect the final FCIR images and their interpretations. For example, the faded green areas at the polychrome ceiling of Cusiuhiriachi, appeared in FCIR with a light blue hue suggesting the presence of a copper



**Figure 5.** VIS and FCIR images details from the case studies ceilings: Santa Maria de Cuevas (a); Cusiuhiriachi (b); San Francisco de Borja (c) and Santa Ana de la Joya (d). Isaac Rangel-Chávez, Instituto de Física, UNAM, 2016.



based green pigment. Also of note are areas that have been exposed to water damage. In these cases, the greenish details became darker resulting in a darkish pale blue in IR-FC, which should mean that a green earth pigment could have been used. In contrast, the dark green leaves that decorate the semi vertical panels that border the ceiling appear as dark blue to almost black with a reddish tone in IRFC. These variances between the central panels and the side panels suggest that two different pigments made of different materials could have been used.

The same variations were also observed in the case of ANA. Small green crystals encrusted between small yellowish-green particles were seen over LM. The sample taken from a water damaged area shows the green compacted particles fading into a dirty white to brownish colour tone. In the case of SMC, a large white-transparent particle with visible fibre structure was observed on the surface of one of the green samples from the nave ceiling. These particles are well identified and associated with those seen in natural malachite under the microscope (Bevilaqua, Borgioli, and Gracia 2010, 117). Similar small crystals were observed in other case studies, however not as clearly as in the green samples from Santa Maria de Cuevas. All green points analysed by XRF contain copper (Cu). Arsenic (As) was also detected as a minor component in the green areas only.

The spots analysed by XRF were also studied by FORS. Copper based green pigments such as malachite and copper resinate (copper salts of resin acids), were used as references in the FORS spectra. The spectra from the studied green spots of the SMC ceiling have a similar shape to that of malachite. The FORS spectra of the green spots from CUSI and ANA, however, were not always consistent with the FORS reference spectrum of malachite. The maximum reflectance of the green spots are at 547 nm but the absorption bands are centred at 735 nm while in malachite this band is at 800 nm (Bevilaqua, Borgioli, and Gracia 2010, 241). In these cases, FORS identification for malachite was not clear.

The wall painted frieze from SMC presents different green hues. As mentioned above, XRF analysis found copper as the prevalent element, while arsenic was also detected. It is likely that in this case the colour change is related to light exposure, for example, in the areas that are not directly exposed to the sunlight the colour of the leaves and birds are well preserved. The areas that are exposed to direct daylight from the window have changed the hue to a greenish blue colour (Figure 6).

ATR- FTIR spectra from the studied green samples confirmed the results of the non-invasive techniques. Absorption bands were found in the 1550–1350  $\text{cm}^{-1}$  region, which are related to the carbonate asymmetric stretching vibrational mode. In addition, 890–

670  $\text{cm}^{-1}$  bending bands were observed, which are typically found in hydrated carbonates such as malachite (Adrover García 2001, 38; [www.irug.org](http://www.irug.org)). Although a correlation between the spectra acquired on the churches and the reference (malachite IMP00146 from IRUG database) was good, some discrepancies were also observed. In addition, spectra from the green samples were compared with that of the malachite obtained from the mines located in the geographic area of study and significant differences were found. Interestingly, when this same malachite was used to prepare the pigments applied in the mock-ups, a higher correlation with the spectra obtained from the case studies was observed.

A correlation of 97.78% between ATR-FTIR spectra from the green sample from Santa Maria narthex ceiling and the malachite prepared with indigo (1:1) (Table 2 MI.01) was found, whereas the correlation with the mixture pigment made with yellow reddish earth was only 56.36% (sample VAI. C), but 91.43% with the green from the nave ceiling. This could indicate that two different greens were prepared for the decoration of the nave and the narthex ceilings, since absorption bands from both spectra are similar except for calcium carbonate bands at the narthex green spectra.

According to FCIR image interpretation, in Cusi-huirachi ATR-FTIR results confirmed that two different greens were applied on the ceiling. A 96.70% match between the green from a side panel (dark green at VIS light) and the green prepared with malachite, indigo and yellow earth (sample VAI.B) was found. Whereas, the light green from the central panels presented only a 53% correlation. Most likely, the light green was prepared by malachite (M) (90.19%) with some indigo (92.53%) over calcium sulfate hemihydrate. However, the correlation with the pigment mixture malachite and indigo (MI) was not conclusive (88,50%) (Figure 7).


In Santa Ana, FORS results indicated that the green colours of both areas (narthex ceiling and baptistery), were obtained with a mixture of malachite and an iron (III) hydroxide-oxide based pigment. Nevertheless, no indication of this iron(III) based pigment was observed in the cross sections. ATR-FTIR spectra show correlation with local malachite (83.14/95%) but it is not conclusive.

### 3.2.2. Red & Red-orange

In the FCIR imaging technique, orange-red pigments such as red lead, vermilion and cadmium red, are reported with yellow hues. Iron(III) based pigments such as red ochre have been described in IRFC as: “verde bruno” (brownish green) (Bevilaqua, Borgioli, and Gracia 2010, 259); yellow (Moon, Schilling, and Thirkettle 1992, 49); and brown (Cosentino 2014, 9). In the case of SMC and ANA, the elements preserved their bright colour and appeared in IRFC images as a

Santa María de Cuevas  
Upper frieze - wall paint


M-CH 022-0014

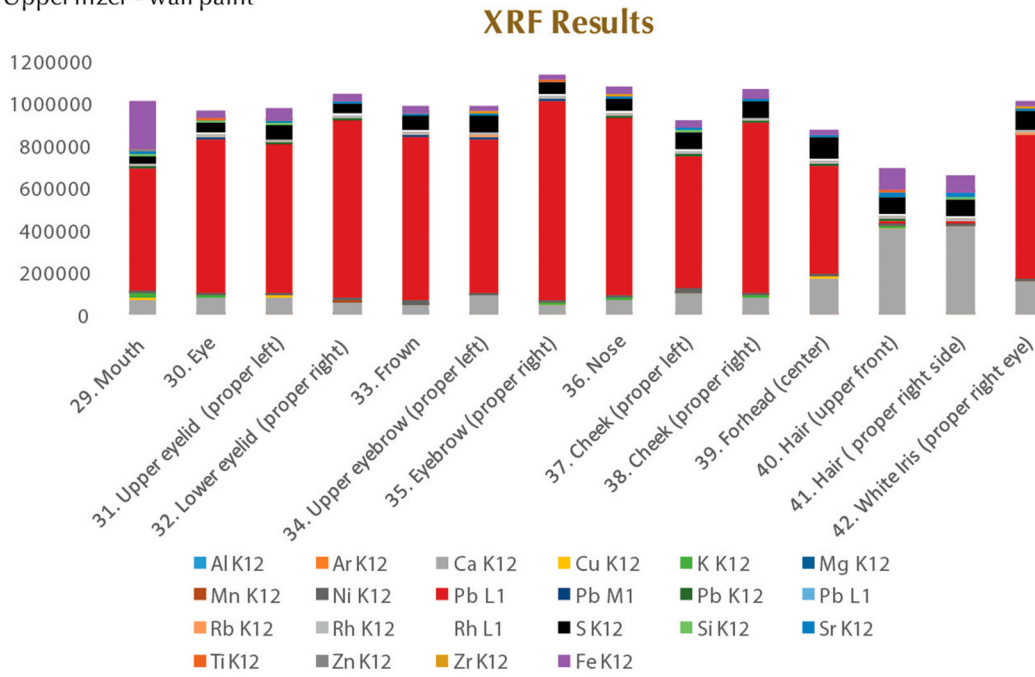

**Figure 6.** XRF chart from the studied spots from the angel face and images from the wall paint upper frieze. It is possible to observe the green malachite from the leaves and birds that have faded into a light blue colour. (E. Casanova, Instituto de Física, Universidad Nacional Autónoma de México, 2016; images: K. Muñoz-Alcocer, 2004; 2016).

bright yellow with some tendency towards a greenish. The areas that were affected by humidity and that have black stains, produce a yellow brownish colour

in FCIR. Again, based on references mentioned before, the red areas from these ceilings are more likely to be made of iron(III) oxide based pigments.

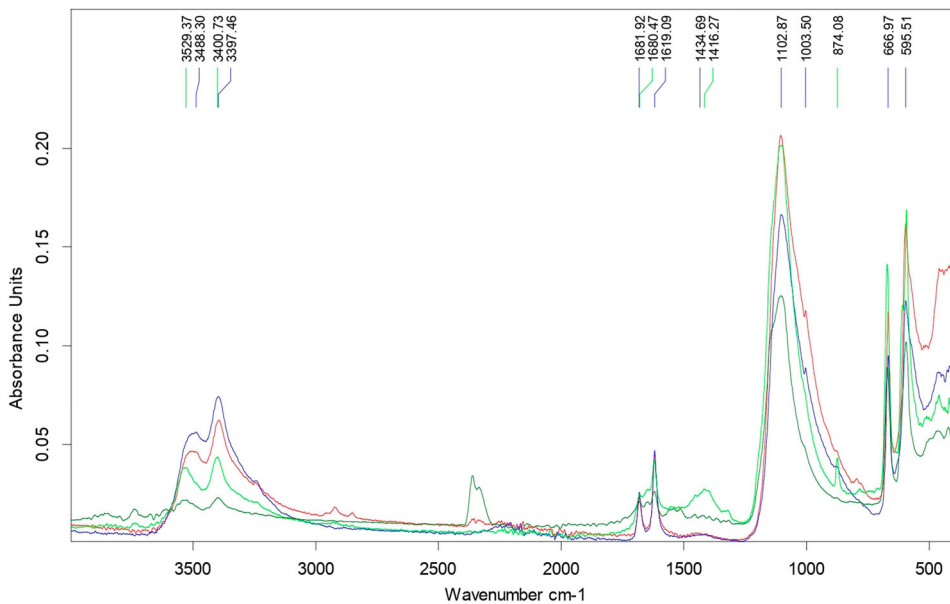

**Figure 7.** ATR-FTIR spectra from the narthex green sample from Santa Maria de Cuevas narthex ceiling (light green line), nave ceiling (dark green line) and the prepared pigments VALC (red line) and MI (blue line) (D.Maldonado, K. Muñoz Alcocer, 2018).



In the case of the wall paint from Santa Maria de Cuevas, XRF detected iron as a major element in the red botanic motifs of the frieze, and lead in the pigment used to render the lips and faces of the two angels. The differences between brightness in the red from ceiling and the red from the botanic ornaments of the frieze are most likely due to the support used. According to previous studies, organic binders do not affect the change of tone or colour in IRFC images, but the concentration of the pigment does (Moon, Schilling, and Thirkettle 1992, 49). This can be clearly seen in the FCIR image of the nave ceiling where the intensity of the hue varied according to the degradation of the colour paint. The angel faces were not sampled as in general these areas are in good condition.

XRF analyses indicate that the red from the Cusi-huirachi and San Francisco de Borja polychrome ceilings presents lead as the major element, which could be associated with the presence of minium. The FORS spectra of those two ceilings confirmed the presence of minium, presenting a reflectance inflexion point at 565–575 nm in accordance with the reference data (Aceto et al. 2012a, 2012b, 2014). In conjunction with these findings and the verification of minium in the ceiling, there were a few cases in which another inflexion point at 580–585 nm is present in addition to the main inflexion point at 570 nm (Leona and Winter 2001). This finding can be related with the presence of small quantities of vermilion in the red pigment (Figure 8).

Both red colours from CUSI's ceiling (flowers and structure) show a yellow – brownish yellow in IRFC imaging with some hue differences (Figure 4b). As in San Francisco de Borja, the red appears to have two subtle hues depending on the concentration of the pigment used. The red in the triangular motifs is an


intense orange applied as one layer, whereas the pigment in the flower motifs was applied in two layers. Both reds appeared yellow in IRFC with some hue differences as well (Figure 4c).

In the ATR-FTIR spectra from Cusi-huirachi red samples from the coffered ceiling wood structure (beams) confirm the presence of minium (absorption bands at 521s, 455s and 398s  $\text{cm}^{-1}$ ) and gypsum (Bevilaqua, Borgioli, and Gracia Rodríguez 2010, 221; Hunt et al. 1950). However, the presence of minium in the red flowers that decorate the board panels was not ascertained. ATR-FTIR spectra were also compared with those collected from a rock acquired from local lead mines. The rock contains a high concentration of minerals containing lead, such as red lead. On this sample absorption bands similar to those observed in the painted samples were found, but they were not sufficient to determine the presence of minium. Due to the strong absorption band at the region (1150s, 1106s, 1096s, 1000md, 782p  $\text{cm}^{-1}$ ), comparisons were also made with an iron(III) oxide based sediment collected a few kilometres from the church, and with commercial pigments. Comparison of the absorption bands indicated that the red flowers were painted with minium combined with iron(III) oxide based sediments.

### 3.2.3. Black

Black coloured materials were used in the four case studies to outline the botanic ornaments and figures. The analysis of these black areas was difficult due to the fact that black hue is mostly overlapping other colours.

XRF and FORS techniques obtained almost similar results in the four case studies. The elements detected by XRF were most likely representative of the background colour beneath the black line, while in areas where black was not overlapping another colour, the

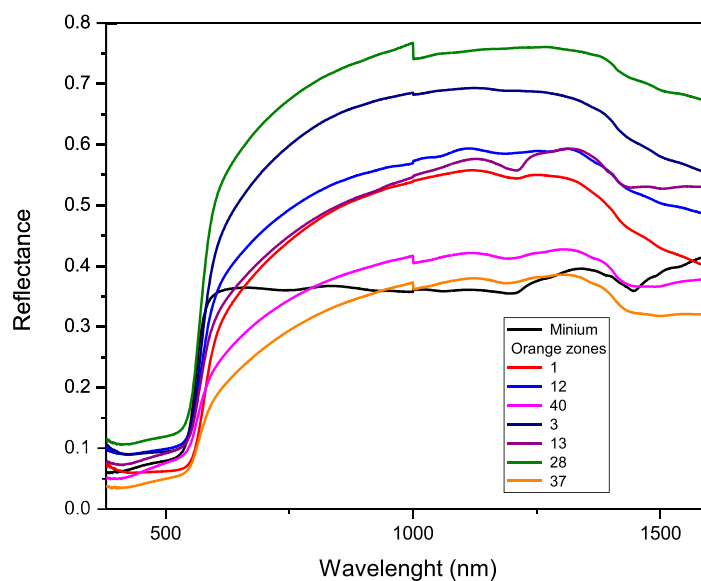

**Figure 8.** Detail view from San Francisco de Borja polychrome ceiling and FORS spectra from the red-orange studied spots. Minium reference (black line) red-orange spots studied (colour lines). (M.A Maynes, Institut of physic, Universidad Nacional Autónoma de Mexico, 2016).

elements detected were probably associated to the ground layer. However, an increase of iron, manganese and potassium was observed in some cases. No identification of the black pigment was determined by FORS. These results could indicate that carbon black was used at the polychrome ceiling of the four case studies. Nevertheless, ATR-FTR spectra indicated that a mixture with carbon black (burnt wood) and local black earth had been used to prepare the black, especially at ANA, which will be explained in more detail.

A clear European influence can be seen in the use of black to delineate the figures, as the colour chosen in pre-Hispanic times for this purpose was red, usually manufactured from earth pigments. In this same sense, the Pre-Columbian mural paintings that have been preserved in Mexican territory do not contain evidence of the use of black to create volume in the figures represented (Vázquez de Ágredos Pascual et al. 2018). Therefore, both uses of black refer to European influences in the field of Mexican mural painting that was developed in Colonial times. The tone of umber could vary from blue-grey to a dark brown depending on the area (Figure 4).

One black sample from Santa Ana was observed under the stereoscope. The paint layer appeared compact, made of well adhered powdery black particles. Also visible were small green, red, and yellowish crystals mixed with the black particles and with white-transparent crystals. These particles are not regularly present in carbon black samples. Based on the reported characteristics, the black pigments found at Santa Ana de la Joya appeared to be made with iron oxide minerals (Figure 9).

In two of the three black spots studied by XRF, manganese was detected between the major elements with calcium and iron, including an increase of sulphur and potassium in comparison with those found at the ground layer. The measurement of the third spot was made in a black stain existing at the dark blue colour. The elements found at this spot are the same ones


that are present in the blue studied spots (Ca, S, Fe). According to the elements found at the two black spots, the use of iron – manganese oxide as black pigment is not considered (Pitarch et al. 2014). FORS spectra were not conclusive.

The same black sample observed under the stereoscope was studied by ATR-FTIR. Absorption bands related to calcite were detected from the background, similar to the ground layer. The ATR-FTIR spectrum presents O-H stretching bands at 3524 and 3398  $\text{cm}^{-1}$  and a weak broad band at 3115  $\text{cm}^{-1}$ . Si-O absorption bands (Derrick, Stulk, and Landry 2015, 117) were also identified (1642  $\text{cm}^{-1}$ ). In addition, the spectrum presents strong absorption bands in the 500–400  $\text{cm}^{-1}$  range that could also be related to the presence of iron oxide materials. Based on these correlations with iron oxide pigments, ATR-FTIR results are in correspondence with those obtained by XRF elemental analysis.

To corroborate the results obtained, the spectrum was compared with a commercial iron oxide pigment from Windsor & Newton and with local black earth collected in the region of study. The spectra from the black panel present similar high correlation with both references. The commercial pigment maintained a higher correlation (Quick compare 93/95%) than the local raw black earth (90%). In addition, the spectrum from the black sample was compared with burnt wood, and a high correlation (88%) was found, but not as high as was detected with iron oxide pigments. However the use of a mixture of both organic and inorganic materials could have been used to produce the black pigment at Santa Ana de la Joya (Figure 10).


### 3.3. Binding media in grounds and painted layers

Ground and coloured samples from the case studies were analysed by GC-MS using the two methods, as

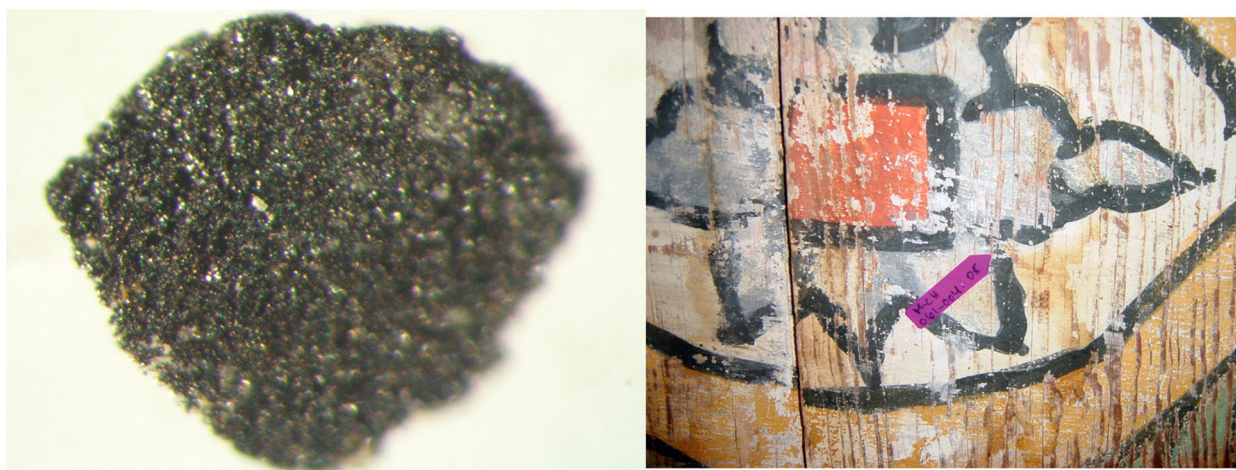

**Figure 9.** Black sample from Santa Ana de la Joya narthex under the microscope and image from the area in which the sample was taken (K. Muñoz-Alcocer, 2018).



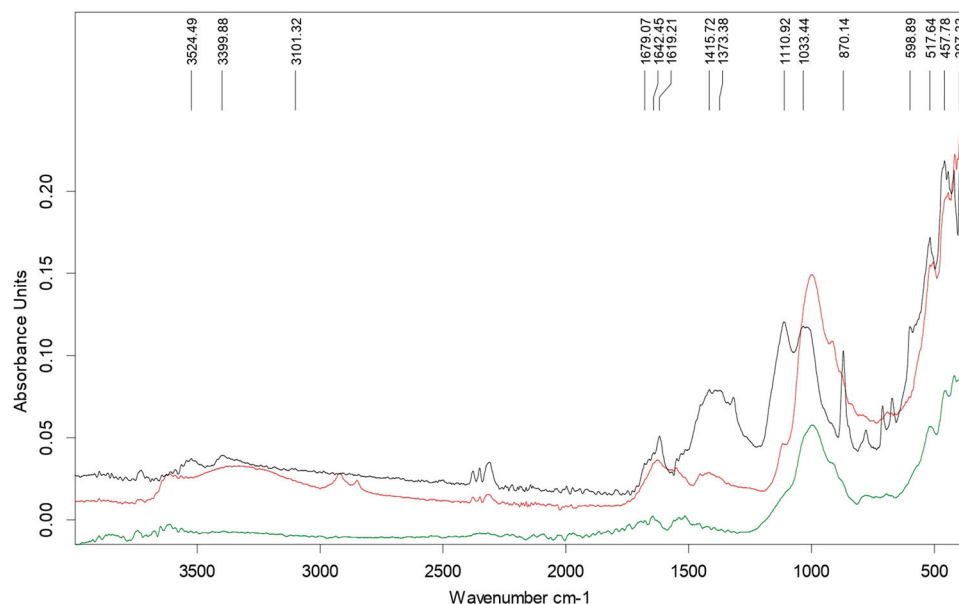

**Figure 10.** Comparison between ATR-FTIR spectra from the black sample B.T.06 (black line), local black earth RM.04 (red line) and burnt wood (green line). (K. Muñoz Alcocer & A. Pizarro, LPH, 2015).

previously described. Generally, samples were very small.

### 3.3.1. Santa Maria de Cuevas


The organic fraction of the ground samples contain traces of lipidic compounds (fatty acids such as palmitic and stearic acids, glycerol), proteinaceous material (amino acids such as alanine, valine, glycine) and carbohydrates (rhamnose, arabinofuranose, arabinose, glucose and gluco-pyranose). Very little variation was found with the colour samples.

The chromatograms obtained from SMC proteins and polysaccharides are similar to the ones detected in the resin-gum of the tascate tree collected in the region around this church. Although the identification needs further analysis, there is a favourable correspondence between the identified compounds (Figure 11).

### 3.3.2. Cusihiuriachi

The organic portion from the Cusihiuriachi samples analysed with both GC-MS methods was very limited. Traces of fatty acids (in particular myristic, palmitic and stearic acids) were identified. The use of drying oils is excluded because of the lack of dicarboxylic acids – typical of the oxidation and polymerization of siccative oils. Their occurrence is likely due to the presence of fatty compounds, such as animal fats.

Analyses of the green paint film by both methods identified a major presence of protein and polysaccharides. The same components were identified in the black samples. As seen for Santa Maria de Cuevas' case study, the GCMS outcomes for Cusihiuriachi have a similar correspondence with the results from the tascate tree exudate.

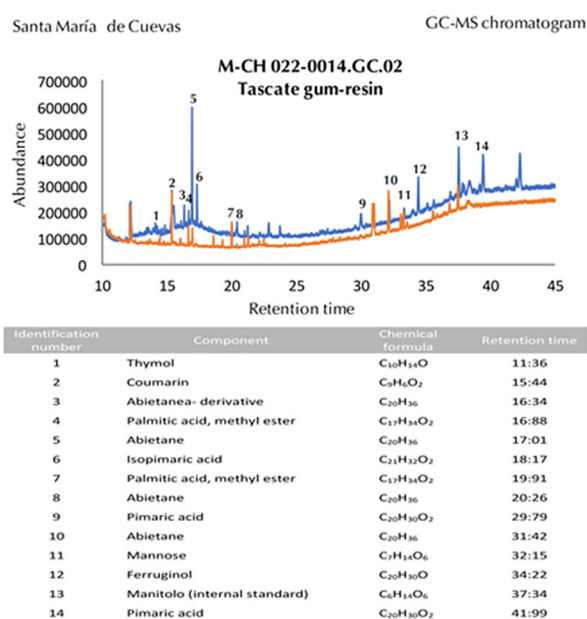

**Figure 11.** GC-MS chromatogram from the ground sample from the panel DT1 (orange line) and the tascate gum (blue line) analysed by the protein method. The table lists the compounds found in the tascate gum-resin. (Performed by F. C. Izzo, P. Consoli & L. Giorgi, 2018).

### 3.3.3. Santa Ana de la Joya

In general, there were no organic components identified as weak peaks, nor were any peaks identified in the C–H region 2990–2850 cm<sup>-1</sup> in the ATR-FTIR spectra from Santa Ana de la Joya. GC-MS was undertaken for two samples in order to determine the presence of a protein as a binder. The samples studied, one from a green layer, and one from a blue layer, were analysed by the protein method. The spectra presented similar components. Traces of protein and polysaccharides were detected; however, the identification was not possible due to the

noise present in the chromatogram. As for San Francisco de Borja, all the ATR-FTIR stretching bands were detected in the region of  $2990-2850\text{ cm}^{-1}$ , indicating the presence of organic molecules. However, the identification was not possible due to the lack of certain absorption bands related to resins and or oils.

### 3.3.4. San Francisco de Borja

GC-MS was undertaken for six samples, in which traces of fatty acids were detected in the ground layer. However, a major presence of proteinaceous and polysaccharide components was also identified. Unfortunately, these analyses were unable to confirm the presence of hydroxyproline as a marker for animal glue. The red sample presented a similar chromatogram to that of the ground layer, showing a major presence of polysaccharide over that of protein. In contrast, the brown pigment showed a significant presence of lipid components mostly related to animal lipids. However, in this case the findings were related to a pigment component and not to the binder.

## 4. Discussion and conclusions

This study demonstrates the local and European influences in the decorative programme of the Mission churches of Santa Maria de Cuevas, Cusihuiachi, San Francisco de Borja and Santa Ana de la Joya. Results from this study show that these influences impacted the design and decorative artistic vision for these interiors, and particularly influenced the selection of raw materials that made the decoration of the polychrome ceilings in these churches possible.

Tascate trees grow in abundance throughout the study area. Several research accounts have been published on the oils that can be obtained from the tascate leaves and branches (Conabio 2000). However, no reference was found about the use of the exudate as a binder for decorative purposes. A significant characteristic of this tree's exudate is a natural property that repels insects and termites. The use of this material as binding medium could explain the good condition of the wooden ceiling. The ground layer has mostly the same characteristics, with minor differences. This could indicate that the resin-gum was applied in the stucco or ground preparation layer.

The components found by GC-MS at the ground layer were also found in the painted layers which could indicate the use of the same gum as binder. In order to determine the presence of tascate gum at the ground and paint layers, mock-ups were prepared using gypsum, tascate resin-gum and water from the river that runs through the town of Santa Maria. This result was also corroborated by the ATR-FTIR technique as the spectra collected on two samples showed a strong correlation (96%)

with the resin-gum reference spectrum. However, further analysis is needed to determine if this resin-gum was applied only at the ground layer or if it was also used as a binder to prepare the coloured material (Figure 12).

The palette is quite similar in all case studies, except for San Francisco de Borja, which is limited to yellow, red, brown-turnsole and black. The absence of green, pink and blue at San Francisco de Borja was not because the artist had no access to these pigments and dyes but because colours were selected as a function of the style of the ceiling structure (Muñoz Alcocer 2018, 419).


Red lead pigment was chosen to paint the ceilings of Cusihuiachi and San Francisco de Borja instead of mixing red and yellow ochre to obtain an orange-red colour, even though they are found in great abundance around these churches. The brightness of red lead was perhaps the reason why it was used in both ceilings.

The presence of mineral lead has been documented in CUSI and SFB. Other red-orange hues, such as those found in the marble imitation paint technique from the beams in Santa Ana and Santa Maria, were made by mixing red ochre and yellow ochre with gypsum. The red and brown from the polychrome ceiling of these two missions were made of red ochre as well. A European influence was also observed in the selection of pigments for the stylistic decoration, as in the ceiling of San Francisco de Borja, upon which red lead was used instead of a local earth. This ceiling seemingly has only Spanish and Italian influences (Muñoz-Alcocer et al. 2017b), since the structure, polychrome design, and pigments come from European style canons. This is opposed to the other case studies, where a fusion of local and European style features and materials was found.

The artistic influences of the New World were detected in the identification of yellow, pink, and blue dyes in Santa Maria de Cuevas (carmines and indigo), Cusihuiachi (plant dye, carmine, indigo), and Santa Ana de la Joya as reported in previous publications (Muñoz-Alcocer et al. 2016, 2017a, 2018).

Historic references suggest that malachite, azurite and turquoise minerals, broadly employed in Mesoamerica since ancient times (Williams & Weigand 1995), were commercialized by the Mogollón culture (1000 BC - 1350 AD) (Haury 1936). The use of malachite as pigment has been registered in central México since Late Pre-classic times (ca. 300 BC - 300 AD). It is presumable that its use was known within northern populations (Vázquez de Ágredos-Pascual et al. 2018). However, no reference on the use of malachite or azurite by Tarahumaras Indians has been found (González Rodríguez 1972; Pennington 1963). Thus, it is reasonable to say that these polychrome ceilings evidence the first use of malachite as a pigment in Chihuahua.



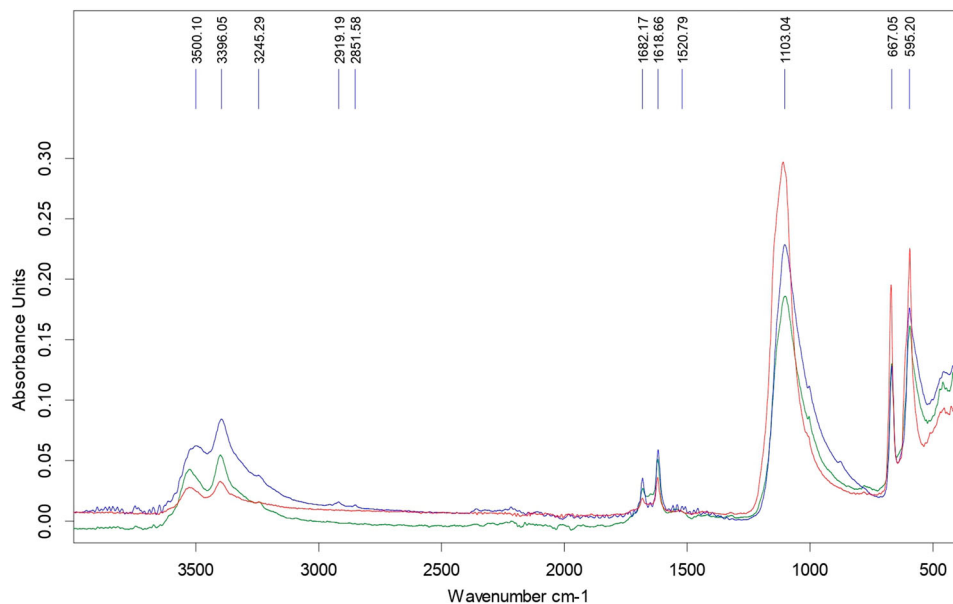

**Figure 12.** ATR-FTIR spectra from Santa Maria de Cuevas nave ground layer (red line), presbytery ground layer (green line), and the ground layer prepared with calcium sulfate anhydrite mixed with tascate resin-gum. (blue line)

Finally, black used as contour lines is present in all the case studies. In Santa Ana, umber was used to create the shape and volume in the decorative motifs, and in Borja, it was included as part of the decoration in alternating black and white squares. The identification of black pigments is complex. XRF and FORS did not provide a clear identification. The presence of manganese in low concentration in the XRF data discarded the possible presence of manganese black. ATR-FTIR spectra indicate that in most of the case studies a mixture of organic and inorganic components was made to produce the black pigments. A major presence of iron oxide was detected at Santa Maria de Cuevas' presbytery, however some correlation was also found with burnt wood (79%). In Cusiuhiriachi a higher spectral correlation was found with both local black earth (89-91%) and burnt wood (91-93%). In San Francisco de Borja, different correlations were obtained between the two black samples. However, in the black sample from the moulding, in which the black material is found separated from other colours, a high correlation with both, local black earth (91%) and burnt wood (92%), was obtained. In Santa Ana, a low correlation (88%) with carbon black was found in comparison with the other case studies. Presence of silicate materials were found, obtaining a high correlation with local black earth (93%). As mentioned above, iron-oxide black compound was used as pigment until the early twentieth century, which does not correspond to the time period of the ceilings studied. Perhaps through the use of red and brown earth in the region in concert with local knowledge of iron-oxide pigment preparation in pre-Hispanic times for ceramic in Paquimé (Bishop et al. 1998; Rakita and Cruz Antillón 2015; Kindel 2019; Triadan et al. 2018) and in the Tarahumara community (Pennington 1963), a black pigment was

prepared. However, further analysis is needed to determine this, since conclusions cannot be extracted from the few samples.

In conclusion, the results presented reveal that polychrome wooden ceilings and decorative walls at Santa Maria de Cuevas, Cusiuhiriachi, San Francisco de Borja, and Santa Ana de la Joya are the evidence of the two principal Jesuit characteristics. First, the adaptation of their own paradigm (*il modo nostro*) to create an architecture that brings local influences together with their own cultural background and conception, as both a religious order and bastion of Spanish culture (Sale 2003). The second is the interest in creating meaningful and magnificent spaces for conversion and evangelization, not only for the new Christians, the natives, but also for the religious Spaniard community that was settling and building a new life on the other side of the ocean (Tellechea and González 2007; González Rodríguez 1995).

## Acknowledgements

The authors are grateful to all the organisations and institutions in Mexico (Misiones Coloniales de Chihuahua A.C., Tecnológico Monterrey Campus Chihuahua, Laboratorio de Patrimonio Histórico, Consejo Nacional de Ciencia y Tecnología – CONACYT, Instituto Nacional de Antropología e Historia – INAH, State Government of Chihuahua, Instituto de Física, Universidad Nacional Autónoma de México (CONACYT LN 293904, LN279740, CB 239609 & PAPIIT UNAM IN112018), Centro de Investigación de Materiales Avanzados – CIMAV Chihuahua, as well as local authorities and members of the communities of Santa Maria de Cuevas, Cusiuhiriachi, La Joya, Rosario, Coyachi, San Francisco de Borja, Satevo), USA (Smithsonian Museum Conservation Institute, J. Paul Getty Grant Program), Spain (Universidad Politécnica de Valencia) and Italy (Università Ca'Foscari Venezia, IFAC-CNR in Firenze)

which have contributed to the development of this study. The GC-MS analytical studies were possible thanks to the group effort of Pasquallina Consoli and Lucia Giorgi. The indigo from Oaxaca was donated by Miguel Angel Maynez PhD, thanks to his donation the characterisation of the green colour was possible. A special thank you to Vicky Karas for her collaboration and contribution in the production of this article.

## Disclosure statement

No potential conflict of interest was reported by the author(s).

## Notes on contributors

**Karla Muñoz-Alcocer** has a PhD on Conservation and Restoration of Cultural Heritage at the Universidad Politécnica de Valencia, Spain. Founded the interdisciplinary project “A Mission for Chihuahua: Its Colonial Missions” serving as director of the nonprofit Misiones Coloniales de Chihuahua since 2000. In 2011 establish the first laboratory focused on science conservation research of cultural heritage in Northern Mexico. Over seven years worked at the Smithsonian Institution as conservator and director of the project *Imaginería de Las Californias* which studied the Spanish colonial polychrome sculpture from Southwest of United States and northern Mexico. Currently she works as professor at Tecnológico de Monterrey Campus Chihuahua.

**Laura Fuster-López** graduated in Fine Arts, specializing in Conservation and Restoration of Cultural Heritage from Universitat Politècnica de València (UPV) where she also got her PhD in Conservation after several internships at Istituto Centrale per il Restauro (Italy) and the Smithsonian Institution (USA). Since January 2005 she is an associate professor at UPV where she also coordinates the research area on the study of the mechanical and dimensional properties of cultural materials, being the relationship between chemical composition and mechanical failure in paintings her current field of study. Since 2016 she is referee for the Spanish Research Agency and for different research programs of the European Commission.

**Ma. Luisa Vázquez de Ágredos-Pascual** is D. Phil. in Geography and History (Universidad de Valencia 2006) and D. Phil in History of Art (Universidad Politécnica de Valencia 2007). Her research focuses on archaeometric and cultural studies of Maya mural painting. Recently, in order to understand their compositions and cultural significances, she has concentrated on physical-chemical analysis of the colors, aromatics and drugs in Pre-Columbian Mesoamerica and other ancient cultures. She is author of numerous articles in specialized journals, such as *Archaeometry*, *Journal of Archaeological Science*, *Journal of Cultural Heritage*, *Analytical Chemistry*, book chapters and books in prestigious publishing, such as Universidad Nacional Autónoma de México, the British Archeological Reports, Cambridge University Press, New Mexico University Press, among others.

**Francesca Caterina Izzo** graduated in “Chemical Sciences and Technologies for the Conservation of Cultural Heritage” at Ca’ Foscari University of Venice with a thesis related to Contemporary Italian Mural Painting. During her European PhD, she did a 1-year internship at RCE (Amsterdam), collaborating with the Modern Oil Project. From 2012 she is an

academic researcher in Conservation Science for Contemporary Art in Venice, focusing on the study of contemporary paintings and Design objects.

**Marcello Picollo**, Ph.D. in Photonics from the University of Eastern Finland (UEF), Faculty of Science and Forestry, Joensuu (Finland) and graduated in geology from the University of Florence, is a researcher at the Institute of Applied Physics “Nello Carrara” of the National Research Council of Italy (IFAC-CNR), Florence. He has been working on spectroscopic investigations of works of art since 1991 and his main research focus is on artists’ material characterization using non-invasive spectroscopic and imaging techniques.

**Giovanni Bartolozzi** is a fellow at the Institute of Applied Physics Nello Carrara of the National Research Council of Italy (IFAC-CNR), Florence. He has been involved for many years in pharmaceutical and agrochemical drug discovery research. From 2011 he has been working on identification and characterization of artists materials using both invasive and non-invasive spectroscopic techniques. Lately he has been involved in a research project dealing with fiber optic pH sensor.

**Jose Humberto Vega**, PhD, was born in Chihuahua, Mexico, his specialty is Botany. He obtained his Doctorate with Cum Laude mention in 2014 from the Autonomous University of Nuevo León. Currently, he is dedicated to teaching and research and has been assigned since 2016 to the Faculty of Zootechnics and Ecology of the Autonomous University of Chihuahua. His research areas are about plant diversity in arid zones and forest in northern Mexico and plant taxonomy. The author currently has five scientific articles indexed in international impact journals, three articles in peer-reviewed journals and has directed four bachelor’s level theses. Dr. Vega is Coordinator of the Grassland Plants Identification Club, which competes annually in different parts of the United States, recently obtaining 3rd place for Mexico. Finally, the Teacher-researcher is the curator of the HUACH-HER Herbarium of the Autonomous University of Chihuahua.

**Diana Maldonado Escobar** is a Biotechnology Engineer graduated from Tecnológico de Monterrey Campus Chihuahua, she specialized in Molecular Biology and also got a *Green Belt- Lean six sigma* certification, which has allowed her to grow up professionally in industrial quality field. During her career, she always show a lot of interest in subjects such as tissue culture, analytical chemistry and genetics, she attend the *Biotechnology of plants in agri-food industry* course at Universidad Complutense de Madrid. Diana got involved in different student groups of biotechnology and she also provided professional social service in the Historical Heritage Laboratory where she contributed with scientific researches mainly sampling and using Fourier Transform Infrared Spectroscopy technique. Currently her professional objective is to continue developing in industrial quality and agricultural biotechnology area.

**Alejandro Mitrani**, B.Sc. in Physics (2008, UABC, Mexico), M.Sc. in Physics (2011) and Ph.D. in Material Science and Engineering (2017), both programs from the Universidad Nacional Autónoma de México (UNAM). He joined the National Laboratory of Sciences for the Research and Conservation of Cultural Heritage (LANCIC), of the Physics Institute, UNAM, for his Ph.D. studies in 2012, and has worked there as an Academic Technician since 2017. While at LANCIC, he has focused in the application of diverse spectroscopic and imaging techniques (such as XRF, PIXE, RBS, SEM-EDS, Raman, FTIR and FORS) for

the non destructive, in situ study of a variety of Mexican cultural heritage materials (including ceramics, metals, gilded objects, glasses, lithic materials and paintings) with ages ranging from Prehispanic all the way to modern objects.

**Dr Miguel Ángel Maynez**, PhD is a member of the National Researchers System in Mexico City, working now in a post-doctoral position in the Aesthetics Institute in the Mexican National and Autonomous University (UNAM in Spanish). Originally formed as a chemistry Miguel Maynez finished in 2012 a master in Material Science and specialized in art material researcher in his doctoral degree. Dr. Maynez has worked with natural organic historical dyes, as a part of his research work he imitated Mexican pre-Hispanic and Colonial recipes taken from ancient codex and historical sources for one hand and for and other the by contemporary artisan workshops in different parts of Mexico.

**Dr Edgar Casanova-González** with a background on Radiochemistry (B.Sc., 2000 and M.Sc., 2006, ISCTN, Cuba) and a Ph.D. on Materials Science and Engineering by the Universidad Nacional Autónoma de México (UNAM), Mexico, he is currently a CONACyT Researcher at the National Laboratory of Sciences for the Research and Conservation of Cultural Heritage, at the Physics Institute of the UNAM. Over the last decade his research has been dedicated to the development and application of non-destructive and portable analytical techniques for the study of cultural heritage. Such techniques include Raman, SERS, FTIR, XRF and FORS spectroscopies, together with imaging methods, applied for the analysis of a wide variety of materials: lithic, panel, mural and easel paintings, manuscripts, ceramics, pigments and dyes and cave paintings, from pre-Hispanic period until modern times.

**Isaac Rangel-Chávez** graduated from the Bachelor of Design and Visual Communication at the Faculty of Arts and Design at UNAM. He is currently a student of the Master in Art History at the Faculty of Philosophy and Letters at UNAM. Linked to the National Laboratory of Sciences for the Research and Conservation of Cultural Heritage (LANCIC) with the thesis: "Methodology for the study of pigments and dyes in works of art and cultural heritage using the false color infrared imaging technique". Since 2016, he collaborates in the Imaging area of LANCIC-IFUNAM implementing the techniques of false color infrared imaging, UV-induced visible luminescence, infrared reflectography, thermal imaging, photogrammetry, orthoimage, false color DStretch, photographic record of samples, materials of reference and study objects.


**Dr Jose Luis Ruvalcaba-Sil** studied Physics at the Sciences Faculty of the Universidad Nacional Autónoma de México (UNAM), and carried out his Ph.D. in the Laboratory of Analyses by Nuclear Reactions in Namur, Belgium. Since 1997, he has been research scientist and professor at the UNAM's Physics Institute. Head of the Pelletron Accelerator facility of this Institute from 2005, from 2014 he is the Head of the National Laboratory of Sciences for Research and Conservation of Cultural Heritage (LANCIC) of Mexico. In particular, his research has been focused on the application of non-invasive methodologies such as XRF, Raman, FTIR, FORS; and the development of spectroscopic instruments of XRF, XRD and PIXE for material characterization of Mexican cultural heritage collections from the pre-Hispanic period to Modern Art in the most important archaeological sites and museums of Mexico in collaboration with groups of UNAM, National Fine Arts Institute (INBA) and the National Institute of Anthropology and History (INAH).

## ORCID

**Karla Muñoz-Alcocer**  <http://orcid.org/0000-0002-7259-5563>

**Jose Humberto Vega**  <http://orcid.org/0000-0001-7488-3334>

**Laura Fuster-López**  <http://orcid.org/0000-0001-7072-7190>

**Ma. Luisa Vázquez de Ágredos-Pascual**  <http://orcid.org/0000-0002-4433-8850>

**Francesca Caterina Izzo**  <http://orcid.org/0000-0001-9319-5094>

**Marcello Picollo**  <http://orcid.org/0000-0003-1012-6048>

**Alejandro Mitrani**  <http://orcid.org/0000-0002-0877-5033>

**Edgar Casanova-González**  <http://orcid.org/0000-0002-4574-9416>

**Jose Luis Ruvalcaba-Sil**  <http://orcid.org/0000-0003-1431-3019>

## References

- Aceto, M., A. Agostino, G. Fenoglio, P. Baraldi, P. Zannini, C. Hofmann, and E. Gamillscheg. 2012a. "First Analytical Evidences of Precious Colourants on Mediterranean Illuminated Manuscripts." *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 95: 235–245.
- Aceto, M., A. Agostino, G. Fenoglio, M. Gulmini, V. Bianco, and E. Pellizzi. 2012b. "Non Invasive Analysis of Miniature Paintings: Proposal for an Analytical Protocol." *Spectrochimica Acta Part A: Molecular and Biomolecular Spectroscopy* 91: 352–359.
- Aceto, M., A. Agostino, G. Fenoglio, A. Idone, M. Gulmini, M. Picollo, ... J. K. Delaney. 2014. "Characterisation of Colourants on Illuminated Manuscripts by Portable Fibre Optic UV-Visible-NIR Reflectance Spectrophotometry." *Analytical Methods* 6 (5): 1488–1500.
- Adrover García, I. 2001. *Applicazioni Della Spettrofotometria IR Allo Studio dei Beni Culturali*. 1er ed. Vicenza: Il prato.
- Appolonia, L., D. Vaudan, V. Chatel, M. Aceto, and P. Mirti. 2009. "Combined use of FORS, XRF and Raman Spectroscopy in the Study of Mural Paintings in the Aosta Valley (Italy)." *Analytical and Bioanalytical Chemistry* 395 (7): 2005–2013.
- Bacci, M., L. Boselli, M. Picollo, and B. Radicati. 2009. "UV, VIS, NIR Fibre Optic Reflectance Spectroscopy (FORS)." In *Practical Hand-Book on Diagnosis of Paintings on Movable Support, European Project ARTECH*, edited by D. Pinna, M. Galeotti, and R. Mazzeo, 197–200. Firenze: Centro Di, Firenze.
- Berdan, F. F., and J. De Durand, eds. 1980. *Matricula de Tributos*, Akademische Druck-Und Verlagsanstalt, Graz.
- Bevilaqua, N., Leonardo Borgioli, Imma Adrover Gracia. 2010. *I Pigmenti Nell'arte: Dalla Preistoria Alla Rivoluzione Industriale*. Saonara: Il prato.
- Bishop, Ronald L., Daniela Triadan, M. James Blackman, and Eduardo Gamboa Carrera. 1998. Production and Distribution of Polychrome Ceramics in the Casas Grandes Region, Chihuahua, Mexico. Paper presented at the 63rd Annual Meeting of the Society for American Archaeology, Seattle.
- Cennini, C. A. 1954. *Il Libro Dell'Arte* (The Craftman's Handbook). Translated and edited by D.V. Thompson. 2nd ed. New York: Dover Publications.
- Conabio. 2000. 'Juniperus deppeana definition'. *Nomenclatur Botanicus*. Segunda Comisión Nacional



- para el conocimiento México uso de la biodiversidad en SIRE paquetes Tecnológico, *Juniperus deppeana* pp. 1–4.
- Cosentino, A. 2014. "FORS Spectral Database of Historical Pigments in Different Binders" [Online]. *E-Conservation Journal* 2: 53–65. <http://e-conservation.org/issue-2/36-FORS-spectral-database> [Consulted: April 17, 2018].
- Dahlgren De, Jordan. 1954. *La Mixteca: su cultura e historia prehispánicas*, Imprenta Universitaria. México.
- Derrick, R., D. Stulk, and J. Landry. 2015. *Infrared Spectroscopy in Conservation Science*. 1st ed, Vol. Scientific Tools for Conservation. Los Angeles, CA: J. Paul Getty Trust.
- de Sahagún, B. 1577. "Historia General de las Cosas de Nueva España: el Códice Florentino" Libro IX: de los mercaderes." Biblioteca digital mundial, Biblioteca Laurenciana, Florencia Disponible en: <https://www.wdl.org/es/item/10620/> [Consulted: 16 January 2016].
- Doener, M. 1984. *The Materials of the Artist and Their Use in Painting: With Notes on the Techniques of the Old Masters, Revised Edition*. 1st ed. Houghton: Mifflin Harcourt.
- Doménech Carbó, Antonio, María Antonio, Cristina Vidal Teresa Doménech, Carbó, María Lorenzo, Laura Osete Luisa Vázquez De Ágredos Pascual, Francisco Cortina, and Valle Algarra. 2014. "Discovery of Indigoid-containing Clay Pellets from La Blanca: Significance with Regard to the Preparation and Use of Maya Blue." *Journal of Archaeological Science* 41: 147–155.
- Fuster Lopez, L., F. C. Izzo, M. Piovesan, D. Yusa Marco, L. Sporni, and E. Zendri. 2016. Study of the Chemical Composition and the Mechanical Behaviour of 20th Century Commercial Artists' oil Paints Containing Manganese-Based Pigments." *Microchemical Journal* 124: 962–973.
- Gettens, R. J. 1962. "An Unsolved Problem in Ancient Pigments." *American Antiquity* 27: 557–564.
- Gettens, R. J., and G. L. Stout, eds. 1946. *Paint Materials: A Short Encyclopedia*. New York: D. van Nostrand.
- González Rodríguez, S. 1972. "Las barrancas tarahumaras" [En línea] e-Journal Universidad Nacional Autónoma de México Disponible en: [www.ejournal.unam.mx/ehn/ehn05/EHNO0506.pdf](http://www.ejournal.unam.mx/ehn/ehn05/EHNO0506.pdf) [Consulta: 16 julio 2017].
- González Rodríguez, L. 1995. "Thomas de Guadalajara (1648-1720), misionero de la Tarahumara, historiador, lingüista y pacificador." *Estudios de historia novohispana* 15): 9–34.
- Hauy, E. W. 1936. *The Mogollon Culture of Southwestern New Mexico*, (No. 20). Priv. print. for the Medallion, Gila pueblo.
- Hunt, J. M., M. P. Wisherd, and L. C. Bonham. 1950. "Infrared Absorption Spectra of Minerals and Other Inorganic Compounds." *Analytical Chemistry* 22 (12): 1478–1497.
- Hunt, J. M., M. P. Wisherd, and L. C. Bonham. 1950. "Infrared Absorption Spectra of Minerals and Other Inorganic Compounds." *Analytical Chemistry* 22 (12): 1478–1497.
- Izzo, F. C. 2011. "20th Century Artists' Oil Paints: A Chemical-Physical Survey (2011)." PhD thesis, Ca' Foscari University of Venice, pp. 1–219.
- Izzo, F. C., K. V. den Berg, H. V. Keulen, B. Ferriani, and E. Zendri. 2014a. "20th Century Artists' oil Paints: the Case of the Olii by Lucio Fontana." *Journal Of Cultural Heritage* 15: 557–563.
- Izzo, F. C., E. Balliana, F. Pinton, and E. Zendri. 2014b. "A Preliminary Study of the Composition of Commercial Oil, Acrylic and Vinyl Paints and their Behaviour after Accelerated Ageing Conditions." *Conservation Science in Cultural Heritage* 14 (1): 353–369.
- Kindl, O. 2019. "The Colors of the Desert. Ritual and Aesthetic Uses of Pigments and Colorants by the Guachichiles of Northern Mexico." In *Painting the Skin. Pigments on Bodies and Codices in Pre-Columbian Mesoamerica*, edited by E. Dupuy and M. L. Vázquez de Ágredos, 102–126. Mexico City: University of Arizona Press.
- Lebgue Keleng, T. 2001. Flora de las Barrancas del Cobre. Universidad Autónoma de Chihuahua. Facultad de Zootecnia. Informe final SNIB- CONABIO. Proyecto No. R102. México, D. F.
- Leona, M, and J Winter. 2001. "Fiber Optics Reflectance Spectroscopy: A Unique Tool for the Investigation of Japanese Paintings." *Studies in Conservation* 46: 153–162.
- Márquez, Z. 1995. *Pueblos Mineros de Chihuahua*. 1er ed. Chihuahua: Gobierno del Estado de Chihuahua.
- Márquez, Z. 2008. *Misiones de Chihuahua S. XVII México XVIII*. 1st ed. Chihuahua: Secretaria de Educación Pública Mexico D.F.
- Moon, T., M. Schilling, and S. Thirkettle. 1992. "A Note on the use of False-Color Infrared Photography in Conservation." *Studies in Conservation* 37 (1): 42–52.
- Mounier, A., G. Le Bourdon, C. Aupetit, C. Belin, L. Servant, S. Lazare, ... F. Daniel. 2014. "Hyperspectral Imaging, Spectrofluorimetry, FORS and XRF for the non-Invasive Study of Medieval Miniatures Materials." *Heritage Science* 2 (1): 24.
- Muñoz-Alcocer, K., L. Fuster-López, A. Pizarro-Medina, M. Picollo, and G. Bartolozzi. 2016. "Pre-Hispanic Pigments and Italian Renaissance Designs at Spanish Colonial Missions Churches in Northern Mexico." *Color Research & Application* 41 (3): 289–293.
- Muñoz-Alcocer, K. M., L. Fuster-López, J. R. Ruiz Checa, M. Luisa Vázquez de Ágredos Pascual, and M. Luisa. 2017b. "The Narrative Decorative Surfaces at the Spanish Colonial Mission Church of Santa María de Cuevas in Nueva Vizcaya: Where Religion, Art & Science Meet." *European Journal of Science and Theology* 13 (2): 135–146.
- Muñoz Alcocer, K. 2018. "Techumbres policromas en templos jesuitas construidos en Nueva Vizcaya en lo siglos XVII y XVIII. Análisis técnico y puesta en valor." Tesis doctoral, Universidad Politécnica de Valencia.
- Muñoz Alcocer, K., L. Fuster-López, J. R. Ruiz Checa, M. Luisa Vázquez de Ágredos Pascual, F. C. Izzo, D. L. Vega Moctezuma, N. R. Flores Holguín, and J. H. Vega Mares. 2017a. "El uso de recursos naturales locales en la producción de superficies pictóricas decorativas en los templos jesuitas de la Nueva Vizcaya (Chihuahua, México)". ARCHÈ, Universidad Politécnica de Valencia Núms. 11-12
- Pennington, C. 1963. *The Tarahumara of Mexico: Their Environment and Material Culture*. Salt Lake City, Utah: University of Utah Press; pp. 209–212.
- Pitarch, À, J. F. Ruiz, S. F. O. de Vallejuelo, A. Hernanz, M. Maguregui, and J. M. Madariaga. 2014. "In Situ Characterization by Raman and X-ray Fluorescence Spectroscopy of Post-Paleolithic Blackish Pictographs Exposed to the Open air in Los Chaparros Shelter (Albalate del Arzobispo, Teruel, Spain)." *Analytical Methods* 6 (17): 6641–6650.
- Rakita, Gordon F. M., and Cruz Antillón Rafael. 2015. "Organization of Production at Paquime." In *Ancient Paquime and the Casas Grandes World*, edited by Paul E. Minnis and Michael E. Whalen, 58–82. Tucson: University of Arizona Press.

- Sale, G. 2003. *Ignazio e l'arte dei gesuiti*. Jaca Book.
- Sarabia Viejo, M. J. 2004. *La Grana y el Añil. Técnicas Tintóreas en México y América Central*. Seville: Fundación El Monte, Consejo Superior de Investigaciones Científicas.
- Tellechea, J. I., M. R. González, I. Pinedo, P. Lécivain, J. Lacouture, P. M. Lamet, U. Valero, C. Lowney, A. A. Bolado, and J. Oraá. 2007. *Jesuitas: una misión, un proyecto*. Universidad de Deusto.
- Triadan, D., E. G. Carrera, M. J. Blackman, and R. L. Bishop. 2018. "Sourcing Chihuahuan Polychrome Ceramics: Assessing Medio Period Economic Organization." *Latin American Antiquity* 29 (1): 143–168.
- Vázquez de Ágredos-Pascual, M. L., C. Roldán-García, S. Murcia-Mascarós, David Juanes Barber, María Gertrudis Jaén Sánchez, Brigitte Faugere, and Veronique Darras. 2018. "Multianalytical Characterization of Pigments From Funerary Artefacts Belongs to the Chupicuaro Culture (Western Mexico): Oldest Maya Blue and Cinnabar Identified in Pre-Columbian Mesoamerica." *Microchemical Journal*, doi:10.1016/j.microc.2019.104101.
- Vázquez de Ágredos-Pascual, M. L., Cristina Vidal Lorenzo, y Gaspar Muñoz Cosme. 2014. The role of new technology in the study of Maya mural painting: over a century of progress (C. Vidal & G. Muñoz, Eds.), *Artistic Expressions in Maya Architecture: Analysis and Documentation Techniques*, BAR International Series (Archaeopress Pre-Columbian Archaeology), Oxford, England.
- Warda, J., F. Frey, D. Heller, T. Vitale, and G. Weaver. 2011. *The AIC Guide to Digital Photography and Conservation Documentation*. Edited by Jeffrey Warda. 2nd ed. Washington, DC: American Institute for Conservation of Historic and Artistic Works.
- Williams, E., and P. C. Weigand. 1995. *Arqueología del occidente y norte de México*. El Colegio de Michoacán AC.